



Łukasiewicz  
Poznań  
Institute of  
Technology

## Drewno. Prace naukowe. Doniesienia. Komunikaty Wood. Research papers. Reports. Announcements

Journal website: <https://drewno-wood.pl>



### Elastic and Shear Moduli of Poplar Heartwood

Tuğba Yılmaz Aydın\*

Isparta University of Applied Sciences, Isparta, Turkey

#### Article info

Received: 21 April 2025

Accepted: 9 June 2025

Published: 15 September 2025

#### Keywords

ring  
poplar  
ultrasound  
rigidity  
elasticity

The elastic and shear moduli of *Populus canadensis* heartwood were measured, and the influence of annual ring width (ARW) on these moduli was determined. Differences between the heartwood and sapwood moduli were identified by comparing the results with reported data. The moduli were dynamically determined by ultrasonic testing and evaluation. Pressure (2.25 MHz) and shear (1 MHz) waves were propagated to obtain the transmission time, which was used to calculate the ultrasonic wave velocities and then the moduli. The average ARW and density were 2.48 cm and 381 kg/m<sup>3</sup>, respectively. The average elastic moduli in the longitudinal (EL), radial (ER), and tangential (ET) directions, and shear moduli in the LR (GLR), LT (GLT), and RT (GRT) planes were 4728 MPa, 1119 MPa, 407 MPa, 1102 MPa, 579 MPa, and 117 MPa, respectively. Neither good nor moderate relationships between ARW and the moduli were observed in linear regression analysis. According to literature reports, the modulus of elasticity decreases with increasing ARW. However, based on the comparison of reported values for sapwood with the results for heartwood obtained in this study, ER, GLR, and GRT increased with the increase in ARW. It should be noted that no relationship with ARW was found in the case of EL, ET, and GLT.

DOI: 10.53502/wood-206067

This is an open access article under the CC BY 4.0 license:

<https://creativecommons.org/licenses/by/4.0/deed.en>.

### Introduction

Reversible deformation under the application of stress, followed by return to the original shape and size when the stress is removed, is a property of elastic behavior. Elastic behavior is a fundamental property for the structural application of natural or engineering materials. Young's modulus, shear modulus, and Poisson's ratios are characteristic elements of elasticity that express how a material responds to different types of stress. The higher the elasticity, the higher the permanent deformation resistance, which is important particularly for structural applications such as load-bearing constructions, as Kamperidou and Vasileiou (2012) described for joints of upholstered furniture frames.

The structure of a material defines its physical properties and mechanical behavior. For example, a crystalline structure presents a regular atomic arrangement and repeating patterns, while an amorphous structure presents an irregular arrangement. The macrostructure (growth rings, early and latewood, and grain orientation), microstructure (cell properties), and chemical structure (cellulose, hemicelluloses, and lignin) of wood make it a natural composite with a polar orthotropic structure. Due to the structure, elastic behavior differs by direction or plane. In general, there are considerable differences between moduli of elasticity in the longitudinal ( $E_L$ ), radial ( $E_R$ ), and tangential ( $E_T$ ) directions, between shear moduli in the LR, LT, and RT planes, and between Poisson's ratios. The orderings

\* Corresponding author: [tugbayilmaz@isparta.edu.tr](mailto:tugbayilmaz@isparta.edu.tr)

of the moduli are generally reported as  $E_L > E_R > E_T$  and  $G_{LR} > G_{LT} > G_{RT}$  (Afoutou et al., 2024; Aydın & Ciritcioğlu, 2021, 2022; Aydın & Yılmaz Aydın, 2020; Güntekin, 2023; Katz et al., 2008; Longo et al., 2018).

The twelve elastic constants of *Populus deltoides* wood were determined by Zahedi et al. (2022) to follow the above-mentioned order. Aydın and Aydın (2023) performed the only study to evaluate the influence of growth ring number and width on the elastic and shear moduli of *Populus x canadensis* wood in the radial direction. The authors determined these features using sapwood samples. However, one of the prominent characteristics of poplar wood is the significant difference in ring widths between the sapwood and the heartwood. Furthermore, even when heartwood, sapwood, mature wood, and juvenile wood all come from the same tree, their mechanical, chemical, and physical characteristics are typically distinct (Bal, 2013) due to the cell structural properties such as wall thickness. In the literature, the mechanical properties of heartwood are reported to be inferior to those of sapwood in the case of *E. grandis* (Bal & Bektaş, 2013), a clone of *Populus deltoides* (Jia et al., 2021), Douglas fir (Duriot et al., 2021), and *Populus usbekistanica* “Afganica” (Bektaş et al., 2020). On the other hand, Xia et al. (2018) reported better physical-mechanical properties for heartwood than for sapwood in the case of *Toona ciliata* M. Roem. Moreover, according to Harte (2009) there is no difference in the mechanical performance of sapwood and heartwood. Therefore, there is no consensus on this issue. Furthermore, when considering the differences between SW and HW, there is no general agreement as to their statistical significance. For example, Merela and Katarina (2013) reported insignificant differences for oak, and Kozakiewicz et al. (2019) found no significant differences for the physical properties of heat-treated black poplar, while Jia et al. (2021) reported significant differences for clones of *Populus deltoides* and *Populus euromaricana* cv. Guariento. Besides these conflicting findings, there are no data presented on the moduli of heartwood in the case of *Populus x canadensis*. It may

be that in industrial practice, timber or laths are not separated as sapwood and heartwood due to production methods and certain other factors, such as profitability. However, from a scientific standpoint, the two parts present different physical, mechanical, aesthetic and other properties. Therefore, this study was carried out to determine the moduli of heartwood and to compare reported sapwood values to evaluate the differences.

## Materials and methods

The study used Canadian poplar (*Populus x canadensis* M.) wood from a plantation tree in Atabey, Isparta, Türkiye. The heartwood section of the radially cut laths was used to cut fifteen samples containing two proper annual rings. Due to variations in the ARW, the sizes of the samples in the radial direction differed from each other (Fig. 1). The longitudinal and tangential sizes of the samples were approximately 20 mm. Samples were acclimatized ( $20 \pm 1$  °C and 65% relative humidity) using a drying chamber (Memmert GmbH+Co. KG, Schwabach, Germany) until their weight stabilized. They were then placed in a desiccator, and density measurements were performed according to TS ISO 13061-2 (2021).

Two elastic constants, modulus of elasticity and shear modulus, were determined non-destructively by ultrasound propagation. Two different wave types (pressure or longitudinal and transverse or shear) were propagated to measure the propagation duration ( $\mu$ s) of the waves in the appropriate axes and planes for elastic and shear modulus determination, respectively. The central frequencies of the pressure and shear waves were 2.25 MHz and 1 MHz, respectively. Contact type transducers, A133S-RM for pressure and V153-RM for shear (Panametrics-NDT, USA), were used with Epoch 650 (Olympus NDT, USA). Wave propagation took place in direct mode. In this procedure, two transducers (a transmitter and a receiver) are placed opposite each other on the specimen surfaces. Official gels were used to optimize decibel (dB) parameters and provide clear peaks.

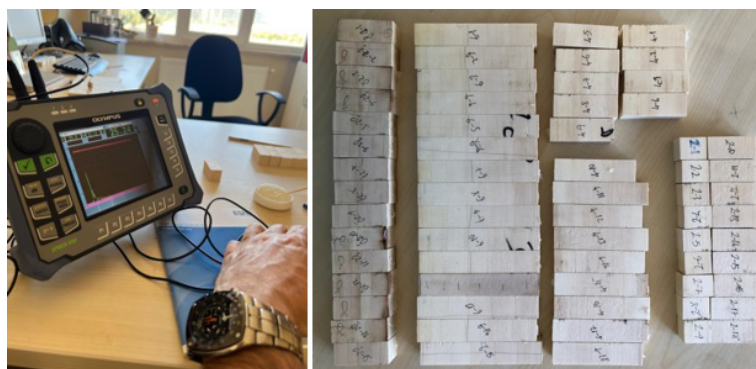


Fig. 1. Ultrasonic measurements (left) and samples (right)

Ultrasonic wave velocities (UWVs) were calculated from the propagation times and path. The elastic and shear moduli were determined by equations (1) and (2), respectively.

$$E_i = \rho V_i^2 10^{-6} \quad (1)$$

where  $E_i$  is the elastic modulus (MPa) in direction  $i$  (L, R, and T),  $\rho$  is the density ( $\text{kg/m}^3$ ), and  $V_i$  is the pressure wave velocity (m/s) in direction  $i$  (L, R, and T).

$$G_{ij} = \rho ((V_{ij} + V_{ji})/2)^2 10^{-6} \quad (2)$$

where  $G_{ij}$  is the shear modulus (MPa) in the  $ij$  plane,  $\rho$  is the density ( $\text{kg/m}^3$ ), and  $V_{ij}$  is the shear wave velocity (m/s) in direction  $i$  with polarization  $j$  (LR, LT, RT, RL, TR, and TL).

A fundamental feature of the structure of poplar wood is the varying ARW. Therefore, the relationships between ARW and the elastic and shear moduli were evaluated by linear regression to determine how well the models estimate the relationship between the variables.

## Results and discussion

The ARW and density of the samples ranged from 2.42 to 2.52 mm and from 356 to 401  $\text{kg/m}^3$ , respectively. Descriptives for the ARW and density are presented in Table 1. Reported average values of ARW for the sapwood of *Populus x canadensis* include 5.37 mm (Ziemiańska & Kalbarczyk, 2018) and 17.7 mm (Aydın & Aydın, 2023). Ziemiańska et al. (2020) reported an ARW of 6.63 mm for *Populus x canadensis*. Considering the notable difference between SW and HW, a 24.8 mm ring width is not unusual. Furthermore, much higher values of ARW have been reported, including 27.8 mm (LeBlanc et al., 2020), 28.6 and 28.8 mm (Šēnhofa et al., 2016), and 45 to 55 mm (DeBell et al., 2002). Such differences depend on many factors that directly affect the tree properties, such as climate, soil conditions, elevation, etc. Moreover, there is a strong relationship between ring width and climatic factors (Šēnhofa et al., 2016); it is found that precipitation and temperature influence the width (Bozkurt & Erdin, 1989). However,

it should be taken into consideration that the place of sampling on the tree significantly affects the values, and hence the means, as Zhang et al. (2022) reported for poplar hybrids. This inference is also valid for density determination. For example, Aydın and Aydın (2023) reported a density range of 335 to 373  $\text{kg/m}^3$  for *Populus x canadensis*, with a mean of 348  $\text{kg/m}^3$ . In another study, the same authors reported an average density of 339  $\text{kg/m}^3$  (Aydın & Yilmaz Aydın, 2024). As seen in Table 1, the HW mean density is 9.57% higher than the SW mean (Aydın & Aydın, 2023). A wider density range (310 to 450  $\text{kg/m}^3$ ) was reported by Flórez et al. (2014). Density means reported in the literature include 365  $\text{kg/m}^3$  (YingJie et al., 2017a), 405.6  $\text{kg/m}^3$  (Hodoušek et al., 2017), 464  $\text{kg/m}^3$  (Villasante et al., 2021), and 529  $\text{kg/m}^3$  (Niklas & Spatz, 2010). Considering the growth conditions, such a wide range for the same species is normal, and the average density determined in this study is in line with the reported values.

The regression model (Fig. 2) revealed that there is no relationship between density and ARW. A similar regression plot for density vs. RW ( $R^2$  from 0.01 to 0.11) was presented by Mankowski et al. (2020) for Scots pine. However, a higher  $R^2$  value (0.31) for density vs. ARW was reported for SW (Aydın & Aydın, 2023). Koga and Zhang (2002) reported that wood density demonstrated no significant correlation with annual growth rate (ring width) in either juvenile or mature wood. Nevertheless, a weakly negative correlation was observed in mature wood. However, it has been hypothesized that wood density is contingent not solely on ARW and latewood proportion, but also on the “quality” of latewood (Vavřík & Gryc, 2012). Furthermore, it has been reported that the relationship between density and climate is stronger and more constant than the relationship between RW and climate (Allen et al., 2012), and the relationship with temperature data was found to be stronger for wood density and RW than for the wood’s anatomical features (Pritzkow et al., 2014). Romagnoli et al. (2014) noted that RW affects the density, although it is sometimes related more strongly to mechanical properties. On the other hand, Zobel and Van Bujten (1989) and Dobrowolska et al. (2011) reported a positive relationship between RW and density. Lars et al. (2005) found that the density of larch heartwood

**Table 1.** Descriptives for Physical properties

|           | ARW (cm) | Density ( $\text{kg/m}^3$ ) |
|-----------|----------|-----------------------------|
| Average   | 2.48     | 381.31                      |
| Std. Dev. | 0.03     | 11.59                       |
| CoV (%)   | 1.14     | 3.04                        |

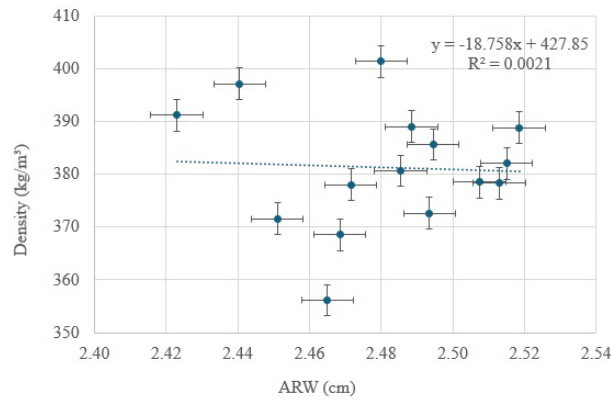


Fig. 2. Regression model for density vs ARW

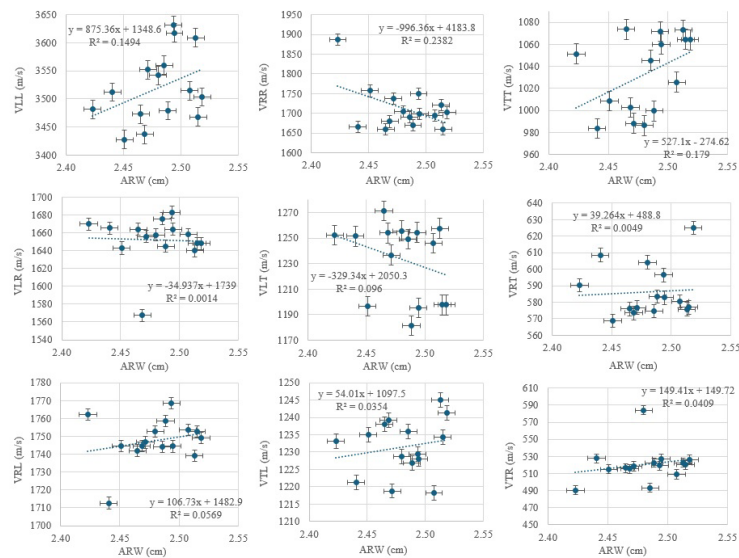


Fig. 3. Regression model for UWV vs ARW

increased with annual ring width up to 2.5 mm and decreased when the ARW was wider than 3 mm.

Averages and descriptives for the velocities are presented in Table 2. In the literature, only Aydın and Yılmaz Aydın (2024) have reported all longitudinal and transverse UWVs for SW, and no data are available for HW. Generally, the UWVs for SW and HW are comparable (with differences of  $-4.8\%$  to  $1.8\%$ ). However, the values of  $V_{RR}$ ,  $V_{TT}$  and  $V_{TR}$  are 20.3%, 14.6% and 7.6% lower than those given in the literature, while  $V_{LR}$  and  $V_{RL}$  are 9.1% and 13.3% higher, respectively. Yılmaz Aydın and Özkan (2024) reported  $V_{LL}$  as 3620 m/s for SW. Aydın and Aydın (2023) reported  $V_{RR}$  as 1607 to 1850 m/s,  $V_{LR}$  as 1463 to 1501 m/s,  $V_{RL}$  as 1491 to 1588 m/s,  $V_{RT}$  as 532 to 565 m/s, and  $V_{TR}$  as 504 to 522 m/s for SW. These values are consistent with the data presented in Table 2. When considering the structural differences between the SW and HW, this variation can be assumed to be normal for wood material. Further differences in reported UWV values may

be mentioned; for example, Zahedi et al. (2022) determined UWVs of *Populus deltoides*, finding differences of  $-28.5\%$  ( $V_{RL}$ ) to  $33.6\%$  ( $V_{TT}$ ).

As Figure 3 shows, there is no relationship between the UWVs and ARW; the  $R^2$  values are extremely low. Similarly low values were also reported by Aydın and Aydın (2023) for SW. However, those authors have also reported much higher  $R^2$  values: 0.57 ( $V_{LR}$  vs. ARW) and 0.64 ( $V_{RL}$  vs. ARW).

Averages and descriptives for the moduli are presented in Table 3. Yılmaz Aydın and Özkan (2024) reported 4549 to 4735 MPa for  $E_L$  (dynamically determined by US) and 5461 to 5910 MPa for MOE in bending. In this study, the range was 4294 to 5046 MPa, and the average  $E_L$  is in line with the results of Aydın & Yılmaz Aydın (2024), who determined the  $E_L$  of *Populus canadensis* dynamically by ultrasound as 4361 MPa. However, considerably higher values (10113 MPa for MOE bending and 10366 MPa for MOE MTG) have been reported for *Populus canadensis* (Hodoušek

**Table 2.** Descriptives of UWV

|                                                           | Longitudinal UWV (m/s) |                 |                 | Shear UWV (m/s) |                 |                 |                 |                 |                 |
|-----------------------------------------------------------|------------------------|-----------------|-----------------|-----------------|-----------------|-----------------|-----------------|-----------------|-----------------|
|                                                           | V <sub>LL</sub>        | V <sub>RR</sub> | V <sub>TT</sub> | V <sub>LR</sub> | V <sub>RL</sub> | V <sub>LT</sub> | V <sub>TL</sub> | V <sub>RT</sub> | V <sub>TR</sub> |
| Average                                                   | 3520.4                 | 1711.9          | 1033.1          | 1652.3          | 1747.7          | 1233.2          | 1231.6          | 586.2           | 520.4           |
| Std. Dev.                                                 | 63.81                  | 57.51           | 35.10           | 26.52           | 12.60           | 29.94           | 8.09            | 15.80           | 20.81           |
| CoV (%)                                                   | 1.81                   | 3.36            | 3.40            | 1.60            | 0.72            | 2.43            | 0.66            | 2.70            | 4.00            |
| Aydın and Yılmaz<br>Aydın (Aydın & Yılmaz<br>Aydın, 2024) | 3585                   | 2060            | 1184            | 1502            | 1515            | 1210            | 1172            | 563             | 560             |

**Table 3.** Descriptives of elasticity and shear moduli

|           | Elasticity Modulus (MPa) |                |                | Shear Modulus (MPa) |                 |                 |
|-----------|--------------------------|----------------|----------------|---------------------|-----------------|-----------------|
|           | E <sub>L</sub>           | E <sub>R</sub> | E <sub>T</sub> | G <sub>LR</sub>     | G <sub>LT</sub> | G <sub>RT</sub> |
| Average   | 4727.89                  | 1118.88        | 407.15         | 1102.13             | 579.07          | 116.94          |
| Std. Dev. | 238.05                   | 89.53          | 25.73          | 41.53               | 19.39           | 9.46            |
| CoV (%)   | 5.04                     | 8.00           | 6.32           | 3.77                | 3.35            | 8.09            |

et al., 2017). Also, Yingjie et al. (2017b) determined a higher value of MOE in bending (9303 MPa) for *Populus canadensis*. Such variation may be attributed to the test procedures and the uniqueness of the wood specimens. The  $E_R$  range and mean for SW of *Populus canadensis*, measured by US, were reported as 705 to 1696 MPa (Aydın & Aydın, 2023) and 1438 MPa (Aydın & Yılmaz Aydın, 2024), respectively. In this study,  $E_R$  ranged from 981 to 1393 MPa, and the average given in Table 3 is in agreement with the literature. Values of  $E_T$  varied from 369 to 440 MPa, and the average is comparable to the 476 MPa reported for SW (Aydın & Yılmaz Aydın, 2024).

The shear moduli  $G_{LR}$ ,  $G_{LT}$ , and  $G_{RT}$  ranged from 1011 to 1167 MPa, 549 to 619 MPa, and 106 to 142 MPa, respectively. Aydın and Aydın (2023) reported ranges of 694 to 912 MPa for  $G_{LR}$  and 83 to 125 MPa for  $G_{RT}$  for SW of *Populus canadensis*, determined by US. Further reported shear moduli for SW of *Populus canadensis* are 771 MPa, 480 MPa, and 107 MPa, respectively (Aydın & Yılmaz Aydın, 2024), different from those obtained in this study by -30.1%, -17.1%, and -8.5%. It was therefore observed that there are reasonable differences between the moduli of SW and HW. Besides *Populus canadensis*, ranges of 872 to 5000 MPa for  $E_R$ , 600 to 2320 MPa for  $G_{LR}$ , and 100 to 470 MPa for  $G_{RT}$  have been reported for different poplar species (Longo et al., 2018; Sliker & Yu, 1993; Zahedi et al., 2022; Zhou et al., 2021).

Values of  $R^2$  between elastic constant and ring width are presented in Figure 4. The coefficients are extremely low and, except in the case of  $G_{LR}$ , are comparable

to the  $R^2$  values for *Populus canadensis* reported by Aydın & Aydın (2023): 0.01 ( $E_R$  vs. ARW), 0.55 to 0.58 ( $G_{LR}$  vs. ARW), and 0.11 to 0.25 ( $G_{RT}$  vs. ARW). There is no reported coefficient for the moduli vs. ARW for *Populus canadensis* to compare; however, 0.88  $R^2$  for MOE vs. ARW for Japanese larch (Wang et al., 2022), 0.21  $R^2$  for  $E_R$  vs. ARW for Norway spruce (Dinulică et al., 2021), and 0.14 to 0.43 and 0.16 to 0.88  $R^2$  for MOE vs. ARW for Scots pine (Mankowski et al., 2020) have been reported. Therefore, the existence of inconsistent values (a wide range of coefficients) makes it difficult to make a meaningful comparison.

Wang et al. (2022) found that RW was negatively correlated with MOE and that RW is more suitable for evaluating MOE than latewood percentage. Moore et al. (2012) determined that MOE decreased with an increase in mean RW for Sitka spruce. Demirkır et al. (2013) found higher MOE in bending for narrow annual rings (5 mm) than for wide annual rings (10 mm) in stone pine. In a study that compared the influence of RW on the moduli for both SW and HW (Aydın & Aydın, 2023), it was observed that the inverse relationship between the RW and moduli was replaced by a positive relationship. However, this relationship is limited to  $E_R$ ,  $G_{LR}$ , and  $G_{RT}$ . Moreover, Dinulică et al. (2021) reported that for Norway spruce,  $E_R$  increases with an increase in mean RW for SW, while Tumenjargal et al. (2019) reported that in larch, the MOE of HW was significantly lower than that of SW. However, it should be noted that there are other factors that influence the moduli, such as sampling location. For



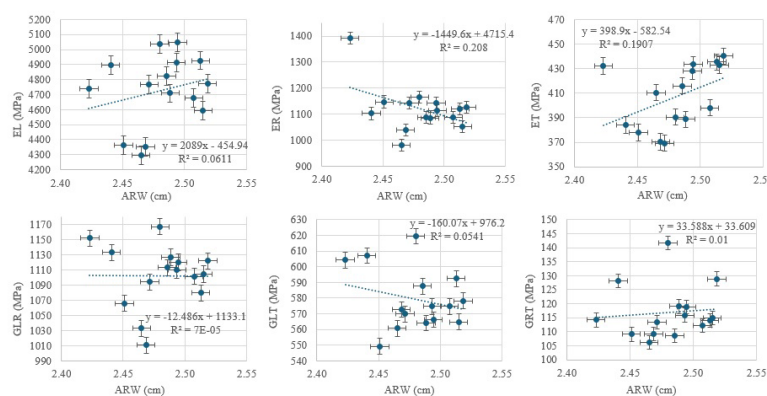


Fig. 4. Regression model for moduli vs ARW

example, MOE increases with an increase in distance from the pith in sentang wood (Ahmad et al., 2023) and in larch (Wang et al., 2022).

Ultrasound propagation in solids such as wood requires attention due to their polar orthotropic nature and natural inhomogeneities in the structure. The propagation properties of P and S waves in a nonhomogeneous porous solid may create some reading difficulties due to phenomena such as dispersion (Saadat-Nia et al., 2011), attenuation, scattering (Bucur, 2006), density, and length interaction (Yılmaz Aydın & Aydın, 2018). In wider growth rings, the share of thick-walled fibers is higher, which positively affects wood density (Arnič et al., 2022). Therefore, when considering structural dissimilarity, even if the samples were prepared from the same log, due to sampling conditions such as location, direction, etc., such variation in the mechanical

properties as determined by ultrasound propagation is reasonable.

## Conclusions

Elastic and shear moduli in three essential axes and planes for the HW of *Populus canadensis* have been dynamically determined, and the influence of ring width on these values has been evaluated. The values of the moduli were in line with those previously reported. Comparing HW and SW, some moduli values tend to slightly increase with an increase in RW, which is in contradiction to the literature. However, due to the lack of reported data for comparison, it could not be determined whether or not the same tendency applies to  $E_L$ ,  $E_T$ , and  $G_{LT}$ . A correlation between ring width and density or modulus values could not be established.

## Conflict of interest

The author(s) declare(s) that there is no conflict of interest concerning the publication of this article.

## References

- Afoutou, J. S., Zhang, X., & Dubois, F. (2024). Full elastic properties characterization of wood by ultrasound using a single sample. *Wood Science and Technology*, 58(1), 403–422. <https://doi.org/10.1007/s00226-023-01525-y>
- Ahmad, M. H., Amini, M. H. M., Sobri, S. A., Sakagami, H., & Hermawan, A. (2023). Effect of radial growth rate on wood properties variation of Sentang (*Azadirachta excelsa*) tree planted in Kelantan, Malaysia. *BioResources*, 18(3), 5013–5027. <https://doi.org/10.15376/biores.18.3.5013-5027>
- Allen, K., Drew, D. M., Downes, G. M., Evans, R., Baker, P., & Grose, M. (2012). Ring width, climate and wood density relationships in two long-lived Tasmanian tree species. *Dendrochronologia*, 30(2), 167–177. <https://doi.org/10.1016/j.dendro.2010.12.006>
- Arnič, D., Krajnc, L., Gričar, J., & Prislan, P. (2022). Relationships Between Wood-Anatomical Features and Resistance Drilling Density in Norway Spruce and European Beech. *Frontiers in Plant Science*, 13. <https://doi.org/10.3389/fpls.2022.872950>
- Aydın, M., & Aydın, T. Y. (2023). Influence of growth ring number and width on elastic constants of poplar. *BioResources*, 18(4), 8484–8502. <https://doi.org/10.15376/biores.18.4.8484-8502>
- Aydın, M., & Ciritcioğlu, H. H. (2021). Comparative study of destructive, nondestructive, and numerical

- procedures for the determination of moisture dependent shear moduli in Scots pine wood. *Materials Testing*, 63(11), 1063–1069. <https://doi.org/10.1515/mt-2021-0041>
- Aydın, M., & Ciritcioğlu, H. H. (2022). Comparative Study of Destructive, Nondestructive, and Numerical Methods on the Determination of Moisture-Dependent Shear Moduli of Calabrian Pine. *Materials Evaluation*, 80(5), 32–41. <https://doi.org/10.32548/2022.me-04228>
- Aydın, M., & Yılmaz Aydın, T. (2020). Moisture dependent elastic properties of naturally aged black pine wood. *Construction and Building Materials*. <https://doi.org/10.1016/j.conbuildmat.2020.120752>
- Aydın, M., & Yılmaz Aydın, T. (2024). Non-Destructive Evaluation of Thermal Treatment Influence on Elastic Engineering Parameters of Poplar. *Drvna Industrija*, 75(4), 405–418. <https://doi.org/10.5552/drwind.2024.0180>
- Bal, B. C. (2013). Even though heartwood, sapwood, mature wood, and juvenile wood all come from the same tree, their mechanical, chemical, and physical characteristics are typically distinct. *Bioresources*, 8(4), 6493–6500.
- Bal, B. C., & Bektaş, İ. (2013). The Mechanical Properties of Heartwood and Sapwood of Flooded gum (*Eucalyptus grandis*) Grown in Karabucak, Turkey. *Ormancılık Dergisi*, 9(1), 71–76.
- Bektaş, İ., Tutuş, A., & Gültekin, G. (2020). The Effect of Sapwood and Heartwood Differences on Mechanical Properties of Fast-Growing Tree Species. *Drvna Industrija*, 71(3), 261–269. <https://doi.org/10.5552/drwind.2020.1940>
- Bozkurt, Y., & Erdin, N. (1989). Ağaç malzeme kalitesi ve silvikültürel tedbirler. *İstanbul University, Faculty of Forestry*, 39(3), 1–13.
- Bucur, V. (2006). Acoustics of wood. In *The Acoustics of Wood* (2nd.). Heidelberg: Springer-Verlag Berlin Heidelberg. <https://doi.org/10.1201/9780203710128>
- DeBell, D. S., Singleton, R., Harrington, C. A., & Gartner, B. L. (2002). Wood Density and Fiber Length in Young Populus Stems: Relation to Clone, Age, Growth Rate, and Pruning. *Wood and Fiber Science*, 34(4), 529–539.
- Demirkı, C., Aydın, İ., Çolak, S., & Çolakoğlu, G. (2013). Effect of width of annual ring on technological properties of plywood panels manufactured from stone pine (*Pinus pinea* L.). *Wood Research*, 58(1), 147–150.
- Dinuliță, F., Bucur, V., Albu, C.-T., Vasilescu, M. M., Curtu, A. L., & Nicolescu, N.-V. (2021). Relevant phenotypic descriptors of the resonance Norway spruce standing trees for the acoustical quality of wood for musical instruments. *European Journal of Forest Research*, 140(1), 105–125. <https://doi.org/10.1007/s10342-020-01318-z>
- Dobrowolska, D., Hein, S., Oosterbaan, A., Wagner, S., Clark, J., & Skovsgaard, J. P. (2011). A review of European ash (*Fraxinus excelsior* L.): implications for silviculture. *Forestry*, 84(2), 133–148. <https://doi.org/10.1093/forestry/cpr001>
- Duriot, R., Rescalvo, F. J., Pot, G., Denaud, L., Girardon, S., & Frayssinhes, R. (2021). An insight into mechanical properties of heartwood and sapwood of large French Douglas-fir LVL. *Construction and Building Materials*, 299, 123859. <https://doi.org/10.1016/j.conbuildmat.2021.123859>
- Flórez, V., Valenzuela, C., Cancino, J., & Acuña, E. (2014). Combining taper and basic wood density equations for estimating stem biomass of the *Populus x canadensis* I-488 variety. *Bosque (Valdivia)*, 35(1), 17–18. <https://doi.org/10.4067/S0717-92002014000100009>
- Güntekin, E. (2023). Determination of elastic constants for Scots pine wood using ultrasound. *Turkish Journal of Forestry*, 24(4), 399–402. <https://doi.org/10.18182/tjf.1294030>
- Harte, A. (2009). *Introduction to timber as an engineering material* (No. 10.1680/mocm.00000.0001). London.
- Hodoušek, M., Dias, A. M. P. G., Martins, C., Marques, A. F. S., & Böhm, M. (2017). Comparison of non-destructive methods based on natural frequency for determining the modulus of elasticity of *Cupressus lusitanica* and *Populus x canadensis*. *BioResources*, 12(1), 270–282.
- Jia, R., Wang, Y., Wang, R., & Chen, X. (2021). Physical and Mechanical Properties of Poplar Clones and Rapid Prediction of the Properties by Near Infrared Spectroscopy. *Forests*, 12(2), 206. <https://doi.org/10.3390/f12020206>
- Kamperidou, V., & Vasileiou, V. (2012). Bending capacity of middle joints of upholstered furniture frames. *Drvna Industrija*, 63(4), 255–261. <https://doi.org/10.5552/drind.2012.1219>
- Katz, J. L., Spencer, P., Wang, Y., Misra, A., Marangos, O., & Friis, L. (2008). On the anisotropic elastic properties of woods. *Journal of Materials Science*, 43(1), 139–145. <https://doi.org/10.1007/s10853-007-2121-9>
- Koga, S., & Zhang, S. Y. (2002). Relationships between wood density and annual growth rate components in balsam fir (*Abies balsamea*). *Wood and Fiber Science*, 34(1), 146–157.
- Kozakiewicz, P., Drożdżek, M., Laskowska, A., Grześkiewicz, M., Bytner, O., Radomski, A., & Zawadzki, J. (2019). Effects of thermal modification on selected physical properties of sapwood and heartwood of black poplar (*Populus nigra* L.). *Bioresources*, 14(4), 8391–8404. <https://doi.org/10.15376/biores.14.4.8391-8404>
- Lars, K., Tommy, M., & Owe, M. (2005). Wood Density, Annual Ring Width and Latewood Content in Larch and Scots Pine. *Eurasian Journal of Forest Research*, 8, 91–96., 8, 91–96.
- LeBlanc, D., Maxwell, J., Pederson, N., Berland, A., & Mandra, T. (2020). Radial growth responses of tulip poplar (*Liriodendron tulipifera*) to climate in the eastern United States. *Ecosphere*, 11(10). <https://doi.org/10.1002/ecs2.3203>

- Longo, R., Laux, D., Pagano, S., Delaunay, T., Le Clézio, E., & Arnould, O. (2018). Elastic characterization of wood by Resonant Ultrasound Spectroscopy (RUS): a comprehensive study. *Wood Science and Technology*, 52(2), 383–402. <https://doi.org/10.1007/s00226-017-0980-z>
- Mankowski, P., Burawska-Kupniewska, I., Krzosek, S., & Grzeskiewicz, M. (2020). Influence of pine (*Pinus sylvestris* L.) growth rings width on the strength properties of structural sawn timber. *BioResources*, 15(3), 5402–5416. <https://doi.org/10.15376/biores.15.3.5402-5416>
- Merela, M., & Katarina, K. (2013). Density and Mechanical Properties of Oak Sapwood Versus Heartwood. *Drvna Industrija*, 64(4), 323–334. <https://doi.org/10.5552/drind.2013.1325>
- Moore, J. R., Lyon, A. J., & Lehneke, S. (2012). Effects of rotation length on the grade recovery and wood properties of Sitka spruce structural timber grown in Great Britain. *Annals of Forest Science*, 69(3), 353–362. <https://doi.org/10.1007/s13595-011-0168-x>
- Niklas, K. J., & Spatz, H.-C. (2010). Worldwide correlations of mechanical properties and green wood density. *American Journal of Botany*, 97(10), 1587–1594. <https://doi.org/10.3732/ajb.1000150>
- Pritzkow, C., Heinrich, I., Grudd, H., & Helle, G. (2014). Relationship between wood anatomy, tree-ring widths and wood density of *Pinus sylvestris* L. and climate at high latitudes in northern Sweden. *Dendrochronologia*, 32(4), 295–302. <https://doi.org/10.1016/j.dendro.2014.07.003>
- Romagnoli, M., Cavalli, D., & Spina, S. (2014). Wood quality of chestnut: Relationship between ring width, specific gravity, and physical and mechanical properties. *BioResources*, 9(1), 1132–1147.
- Saadat-Nia, M. A., Brancheriau, L., Gallet, P., Enayati, A. A., Pourtahmasi, K., & Honarvar, F. (2011). Ultrasonic wave parameter changes during propagation through poplar and spruce reaction wood. *BioResources*, 6(2), 1172–1185.
- Šēnhofa, S., Zeps, M., Matisons, R., Smilga, J., Lazdiņa, D., & Jansons, Ā. (2016). Effect of climatic factors on tree-ring width of *Populus* hybrids in Latvia. *Silva Fennica*, 50(1). <https://doi.org/10.14214/sf.1442>
- Sliker, A., & Yu, Y. (1993). Elastic constants for hardwoods measured from plate and tension tests. *Wood and Fiber Science*, 25(1), 8–22.
- TS ISO 13061-2. (2021). Physical and mechanical properties of wood – Test methods for small clear wood specimens – Part 2: Determination of density for physical and mechanical tests, Turkish Standard Institution, Ankara.
- Tumenjargal, B., Ishiguri, F., Ohshima, J., Iizuka, K., Otsuka, K., Kinomoto, M., & Yokota, S. (2019). Effects of Radial Growth Rate on Wood and Lumber Properties of 67-Year-Old Japanese Larch (*Larix Kaempferi*) Trees Planted in Tochigi, Japan. *Wood and Fiber Science*, 51(3), 264–275. <https://doi.org/10.22382/wfs-2019-025>
- Vavřík, H., & Gryc, V. (2012). Analysis of the annual ring structure and wood density relations in english oak and sessile oak. *Wood Research*, 57(4), 573–580.
- Villasante, A., Vignote, S., Fernandez-Serrano, A., & Laina, R. (2021). Simultaneous treatment with oil heat and densification on physical properties of *Populus × Canadensis* wood. *Maderas. Ciencia y Tecnología*, 24. <https://doi.org/10.4067/S0718-221X2022000100405>
- Wang, S., Chen, D., Chu, J., & Jiang, J. (2022). Effect of Growth Ring Width and Latewood Content on Selected Physical and Mechanical Properties of Plantation Japanese Larch Wood. *Forests*, 13(5), 797. <https://doi.org/10.3390/f13050797>
- Xia, L.-M., Qi, J.-Q., Huang, X.-Y., Xie, J.-L., Xiao, H., Luo, J.-X., ... Song, L.-M. (2018). Physical-Mechanical Properties of Heartwood and Sapwood in *Toona* sp. Wood (*Toona ciliata* M. Roem.) Before and After Accelerated Aging Treatment. *BioResources*, 13(4). <https://doi.org/10.15376/biores.13.4.8409-8420>
- YingJie, Z., DeJun, F., & YanGuang, D. (2017a). Timber physical and mechanical properties of *Populus pyramidalis* Rozier and *Populus × canadensis* cv. “Regenerata.” *Journal of West China Forestry Science*, 46(4), 35–38.
- YingJie, Z., DeJun, F., & YanGuang, D. (2017b). Wood physical and mechanical properties of *Populus × canadensis* Moench and *Populus × euramericana* (Dode) Guinier cv. Gelrica. *Agricultural Science & Technology – Hunan*, 18(12), 2532–2535.
- Yilmaz Aydın, T., & Aydın, M. (2018). Effect of Density and Propagation Length on Ultrasonic Longitudinal Wave Velocity in Some Important Wood Species Grown in Turkey. *Turkish Journal of Forestry | Türkiye Ormancılık Dergisi*, 19(4), 413–418. <https://doi.org/10.18182/tjf.459005>
- Yilmaz Aydın, T., & Özkan, U. (2024). Moisture dependent bending properties of poplar. *Turkish Journal of Forestry | Türkiye Ormancılık Dergisi*, 25(4), 514–517. <https://doi.org/10.18182/tjf.1547421>
- Zahedi, M., Kazemi Najafi, S., Füssl, J., & Elyasi, M. (2022). Determining elastic constants of poplar wood (*Populus deltoides*) by ultrasonic waves and its application in the finite element analysis. *Wood Material Science & Engineering*, 17(6), 668–678. <https://doi.org/10.1080/17480272.2021.1925962>
- Zhang, Y., Fang, S., Tian, Y., Wang, L., & Lv, Y. (2022). Responses of radial growth, wood density and fiber traits to planting space in poplar plantations at a lowland site. *Journal of Forestry Research*, 33(3), 963–976. <https://doi.org/10.1007/S11676-021-01382-0/TABLES/5>
- Zhou, L., Liu, Q., Ma, S., & Han, X. (2021). Eccentric compression behavior of long poplar columns externally reinforced by BFRP. *Journal of Wood Science*, 67(1), 2. <https://doi.org/10.1186/s10086-020-01934-8>
- Ziemiańska, M., & Kalbarczyk, R. (2018). Biometrics of tree-ring widths of (*Populus x canadensis moench*) and



- their dependence on precipitation and air temperature in south-western Poland. *Wood Research*, 63(1), 57–74.
- Ziemiańska, M., Kalbarczyk, R., Chen, J.-R., & Dobrzańska, J. (2020).** Climatic signal in a radial growth of Canadian and Maximovich poplars in south-western Poland. *Scientia Agricola*, 77(5). <https://doi.org/10.1590/1678-992x-2018-0151>
- Zobel, B. J., & van Buijtenen, J. P. (1989).** *Wood Variation – Its Causes and Control*. Berlin, Heidelberg: Springer Berlin Heidelberg. <https://doi.org/10.1007/978-3-642-74069-5>